

Normal-state Hall Angle and Magnetoresistance in quasi-2D Heavy Fermion CeCoIn₅ near a Quantum Critical Point

Y. Nakajima¹, K. Izawa¹, Y. Matsuda¹, S. Uji², T. Terashima²,

H. Shishido³, R. Settai³, and Y. Onuki³, and H. Kontani⁴

¹*Institute for Solid State Physics, University of Tokyo, Kashiwanoha, Kashiwa, Chiba 277-8581, Japan*

²*National Institute of Material Science, Sakura, Tsukuba, Ibaraki 305-0003, Japan*

³*Graduate School of Science, Osaka University, Toyonaka, Osaka, 560-0043 Japan and*

⁴*Department of Physics, Saitama University, Shimo-Okubo, Saitama 338-8570, Japan*

(Dated: February 2, 2008)

The normal-state Hall effect and magnetoresistance (MR) have been measured in the quasi-2D heavy fermion superconductor CeCoIn₅. In the non-Fermi liquid region where the resistivity ρ_{xx} exhibits an almost perfect T -linear dependence, the Hall angle varies as $\cot \theta_H \propto T^2$ and the MR displays a strong violation of Kohler's rule. We demonstrate a novel relation between the MR and the Hall conductivity, $\Delta\rho_{xx}/\rho_{xx} \propto (\sigma_{xy}\rho_{xx})^2$. These results bear a striking resemblance to the normal-state properties of high- T_c cuprates, indicating universal transport properties in the presence of quasi-2D antiferromagnetic fluctuations near a quantum critical point.

PACS numbers: 71.27.+a, 73.43.Qt, 74.70.Tx

The transport and thermodynamic properties in most metals are well described by the conventional Landau Fermi liquid theory. Within the last decade, however, an increasing number of strongly correlated materials, including heavy fermion (HF) intermetallics, organics, and cuprates, have been found to display striking deviations from the Fermi liquid, when they are located close to a quantum critical point (QCP) [1]. In each of these materials, chemical doping, pressure, or magnetic field can tune the quantum fluctuations at zero-temperature. As a result, these systems develop a new excitation structure and display novel thermodynamic and transport properties over a broad temperature range. It is generally believed that the abundance of low lying spin fluctuations near the QCP gives rise to a serious modification to the quasiparticle masses and scattering cross section of the Fermi liquid. In addition, some of these metals show a superconductivity. It appears that in these superconductors many-body effects originating from the strong spin fluctuations associated with the QCP often gives rise to unconventional superconductivity, in which Cooper pairs with angular momentum greater than zero are formed[2]. The relation, therefore, between unconventional superconductivity and quantum criticality emerges as an important issue in strongly correlated systems.

Despite extensive studies on the non-Fermi-liquid behavior in the vicinity of the QCP, many properties in the normal state remain unresolved. In particular the detailed transport properties, *i.e.* how the magnetic excitations influence the transport properties, are unsettled. For instance, in high- T_c cuprates the normal state transport properties above the pseudogap temperature are known to be quite unusual; the resistivity shows a T -linear dependence in a wide T -range, the Hall angle θ_H varies as $\cot \theta_H \propto T^2$ [3], and the magnetoresistance (MR) displays a strong violation of the Kohler's rule [4]. These non-Fermi-liquid features have been controversial because they should ultimately be related to the mech-

anism of the unconventional superconductivity. Therefore, in order to obtain deep insight into such unusual electronic transport phenomena, it is crucial to clarify whether they are universal electronic properties in the vicinity of QCP or are specific to high- T_c cuprates.

Recently a new class of HF compounds with chemical formula CeMIn₅, where M can be either Rh, Ir, and Co, have been discovered [5]. Among them CeCoIn₅ is a superconductor with the highest transition temperature ($T_c=2.3$ K) among all known HF superconductors. The normal state of CeCoIn₅ exhibits all the hallmarks of quantum criticality. The two key parameters of a Fermi liquid, the electronic specific heat coefficient $\gamma = C/T$ and uniform susceptibility χ_0 , increase with decreasing temperature as $\gamma \propto -\ln T$ and $\chi_0 \propto 1/(T + \theta)$, in marked contrast with the T -independent Fermi liquid behavior[5, 6]. Moreover an almost perfect T -linear resistivity[7, 8] is observed from T_c up to 20 K. These non-Fermi-liquid properties have been discussed in the light of the antiferromagnetic (AF) fluctuation near a QCP. In fact the NMR spin-lattice relaxation rate obeys $T_1^{-1} \propto T^{1/4}$, indicating that CeCoIn₅ is situated near an AF instability [9]. Moreover the microscopic coexistence of superconductivity and static AF order has been reported in Ce(Co_{1-x}Rh_x)In₅ and Ce(Ir_{1-x}Rh_x)In₅ systems [10]. It should be noted that CeCoIn₅ has some resemblance with high T_c cuprates. First, the electronic structure is quasi-2D, as revealed *e.g.* by de Haas-van Alphen measurements[6]. Second, the superconducting gap symmetry most likely belongs to the d -wave class, indicating that the AF fluctuation plays an important role for the occurrence of superconductivity [9, 11, 12]. Third, a possible existence of the pseudogap was suggested [13]. In general, extraction of non-Fermi liquid properties near the QCP requires high quality single crystals, since the physical properties are seriously affected by small amounts of disorder induced by the chemical doping or pressure. CeCoIn₅ is suitable for such a pur-

pose because non-Fermi liquid effect can be observed in the undoped compound at ambient pressure. Thus CeCoIn₅ provides a unique opportunity for investigating the transport properties in the presence of strong 2D AF fluctuation in the proximity of the QCP.

In this Letter, we used the Hall effect and the MR to clarify the microscopic scattering mechanism responsible for the unusual physical properties in the quasi-2D HF superconductor CeCoIn₅. The zero field resistivity, Hall effect and the MR, all demonstrate a spectacular breakdown of Fermi-liquid behavior and show a striking similarity to high- T_c cuprates. These results enable us, as mentioned above, to gain strong insights into the transport properties in the presence of the quasi-2D AF fluctuations associated with the QCP.

The high quality single crystals of CeCoIn₅ ($T_c=2.3$ K) were grown by the self-flux method. On cooling from room temperature, $\rho_{xx}(H=0)$ shows a slight increase below ~ 200 K, followed by a crossover to metallic T -dependence below ~ 40 K which seems to correspond to the coherent temperature T_{coh} . Below $T^* \simeq 20$ K ρ_{xx} displays an almost perfect linear T -dependence down to T_c , as shown in the main panel of Fig. 1. The in-plane diagonal (ρ_{xx}) and Hall (ρ_{xy}) resistivities were measured with current $\mathbf{j} \parallel \mathbf{a}$ and $\mathbf{H} \parallel \mathbf{c}$, up to 25 T and up to 14 T, respectively. We obtained ρ_{xy} from the transverse resistance by subtracting the positive and negative magnetic field data. We have measured three different crystals and obtained similar results.

We first discuss the Hall effect. Figure 2(b) depicts the H -dependence of ρ_{xy} . The Hall sign is negative in the present T - and H -range. At high temperatures above 40 K, ρ_{xy} is nearly proportional to H , while at lower temperatures ρ_{xy} shows a distinct deviation from the H -linear dependence. This also can be seen by the inset of Fig. 1, in which ρ_{xy}/H is plotted as a function of T . The data ρ_{xy}/H at $H=0$ are obtained by taking the low field

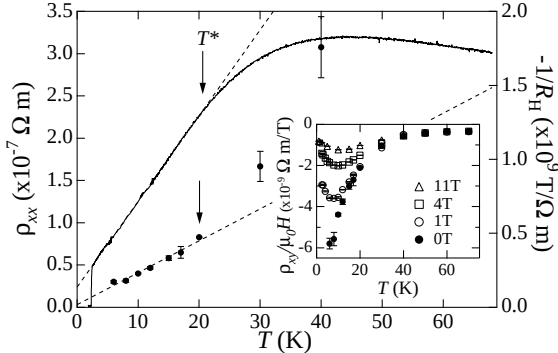


FIG. 1: Main panel: Temperature dependence of $\rho_{xx}(0)$ and $1/R_H$ in zero field limit. The dashed straight lines are guide for eyes. The arrows indicate $T^* \simeq 20$ K, below which T -linear ρ_{xx} and $1/R_H$ are observed. Inset: ρ_{xy}/H vs. T at low fields.

limit of $\frac{d\rho_{xy}}{dH}$. At high temperatures, ρ_{xy}/H is nearly T -independent. As the temperature is lowered, ρ_{xy}/H at $H=0$ decreases monotonically down to T_c , while ρ_{xy}/H at $H \gtrsim 1$ T turns to increase after going through a minimum above T_c . In the main panel of Fig. 1, $1/R_H$ is plotted as a function of T , where $R_H(\equiv \lim_{H \rightarrow 0} \frac{d\rho_{xy}}{dH})$ is the Hall coefficient. A T -linear dependence of $1/R_H$ is observed above T_c up to $T^* \simeq 20$ K, as shown by the dashed line, while a striking deviation from the T -linear dependence is observed at higher temperature. It should be stressed that *the temperature region of T -linear $1/R_H$ coincides nicely with that of T -linear ρ_{xx}* (see arrow in Fig.1), indicating an intimate relation between ρ_{xx} and R_H . The peculiar feature of the Hall effect is further pronounced by plotting the Hall angle $\cot \theta_H(\equiv \rho_{xx}/R_H H$ at $\mu_0 H = 1$ T) vs T^2 , as shown in Fig. 3 [3]. The data fall on a straight line in the temperature range below $T^* \simeq 20$ K and can be quite well fitted as,

$$\cot \theta_H = \alpha T^2 + \beta. \quad (1)$$

A very small "residual" $\cot \theta_H$, $\beta \simeq 0$, is similar to the high- T_c cuprates with low impurity concentration (see Fig. 2 in Ref.[3]). We will discuss the origin of this T -dependence later.

The Hall effect in the conventional HF systems has been studied extensively and is known to exhibit a universal behavior (see Figs. 1 and 2 in Ref. [14]). At high temperatures exceeding T_K , the Kondo temperature, where the f -electrons are well localized with well-

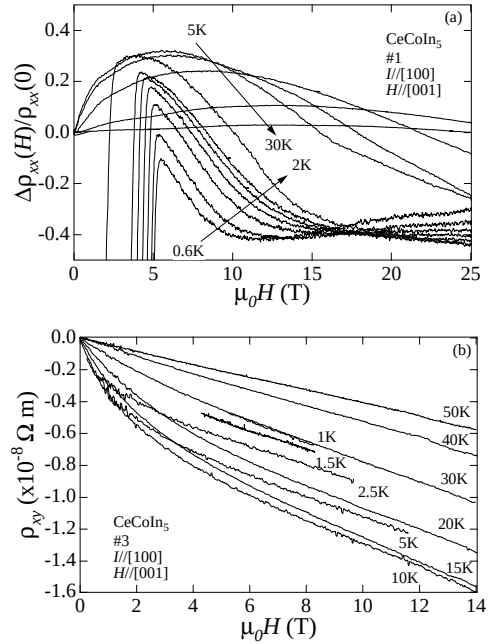


FIG. 2: (a) The magnetoresistance, $\Delta\rho_{xx}(H)/\rho_{xx}(0)$, as a function of H . (b) The field dependence of Hall resistivity $\rho_{xy}(H)$.

defined magnetic moments, R_H is mostly positive and is much larger than $|R_H^n|$ in conventional metals. With the development of the Kondo coherence as the temperature is lowered, R_H decreases rapidly with decreasing T after showing a broad maximum at the temperature $T \lesssim T_{\text{coh}}$. At very low temperature, $|R_H|$ becomes very small and becomes nearly T -independent. These temperature dependence of R_H have been explained as follows. Generally the Hall effect can be decomposed into two terms; $R_H = R_H^n + R_H^a$. Here R_H^n is the ordinary Hall effect due to the Lorentz force and is nearly T -independent within the Boltzmann approximation. Meanwhile R_H^a represents the so-called “anomalous Hall effect” due to skew scattering. The latter originates from the assymetric scattering of the conduction electrons by the angular momenta of f -electrons, induced by the external magnetic field. This term is strongly temperature dependent and well scaled by the uniform susceptibility, $R_H^a \propto \chi_0 \rho_{xx}$ [14, 15] or $\propto \chi_0$ [16, 17, 18], above T_{coh} . The magnitude of R_H^a is much larger than $|R_H^n|$ except at $T \ll T_{\text{coh}}$ where the contribution of the skew scattering vanishes; hence $R_H \simeq R_H^n$ at very low temperatures.

We will show that the Hall effect in CeCoIn₅ shown in Figs. 1 and 2(b) is markedly different from those in ordinary HF systems. The first important signature is that above $T_{\text{coh}} \simeq 40$ K, R_H is nearly T -independent and can be scaled neither by $\chi_0 \rho_{xx}$ nor by χ_0 , both of which have a strong T -dependence above 30 K. In addition, although we do not show here, χ_0 is almost strictly H -linear up to 12 T at $T > 2$ K, while ρ_{xy} shows a nonlinear H -dependence below 30 K as shown in Fig.2(b). Moreover the magnitude of $|R_H|$ above T_{coh} is much smaller than those in other HF systems at high temperatures and in the same order to $R_H(\sim R_H^n)$ at very low temperatures $T \ll T_{\text{coh}}$ where the skew scattering vanishes in other HF systems. Thus both the amplitude and the T -dependence of R_H are obviously in conflict with the conventional skew scattering mechanism. These results lead us to conclude that the skew scattering in CeCoIn₅ is negligibly small

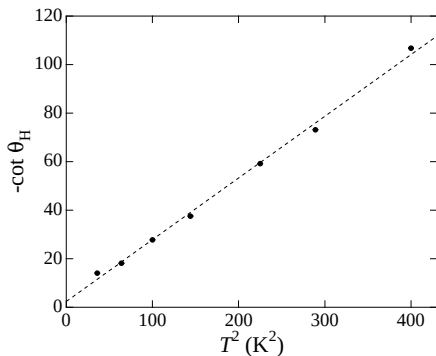


FIG. 3: The Hall angle $\cot \theta_H$ as a function of T^2 . For details, see the text. A fit by $\cot \theta_H = \alpha T^2 + \beta$ gives $\alpha = 0.254 (K^{-2})$ and $\beta = 2.39$ (dashed line)

and T -dependence of R_H mainly stems from the normal part of the Hall effect R_H^n . The absence of skew scattering has also been reported in CeMnIn₅ [19] and double layered Ce₂CoIn₈ [20]. At present the absence of skew scattering in these Ce compounds is an open question. The absence of the skew scattering enable us to analyze the normal Hall effect R_H^n in detail. Having established the evidence of strongly T -dependent R_H^n , which is incompatible with the conventional Fermi liquid theory, we move on to the MR.

The MR in most conventional HF materials also shows a similar behavior [21]. At very low temperature $T \ll T_K$, the MR is positive due to the orbital effect. Then the MR decreases with temperature, changes the sign reaching the negative minimum at $T \sim T_K/2$. The negative MR is due to the suppression of the spin-flop scattering by magnetic field. Figure 2 (a) depicts the MR, $\Delta \rho_{xx}(H)/\rho_{xx}(0)$, as a function of H . A notable MR with an initial positive slope are observed at all temperatures. At high field the MR shows a crossover from positive to negative. The crossover field increases with temperature. Below 2K the MR turns positive at very high field after showing a broad minimum. Thus the MR of CeCoIn₅ displays a peculiar H -dependence, which is very different from ordinary HF systems [23]. The positive MR at very high field below 2 K is most likely to be an usual orbital MR due to the cyclotron motion of the electrons. The negative MR at high field seems to appear as a result of the suppression of the spin-flop scattering, similar to the other HF compounds. The fact that the negative MR can be observed even at 25 T indicates the presence of a characteristic energy scale of the AF fluctuation which corresponds to a few meV. We note that recent scaling argument based on the measurements of C and χ_0 for Ce_{1-x}La_xCoIn₅ suggests a presence of the new energy

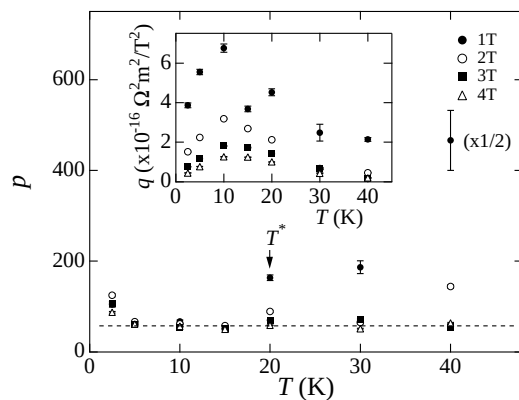


FIG. 4: Main panel: $p(\equiv \Delta \rho_{xx}(H)/\sigma_{xy}(H)\rho_{xx}^3(0))$ is plotted as a function of T at low fields. The modified Kohler's rule represented by Eq.(5) well describes the data below $T^* \simeq 20$ K. Inset: $q(\equiv \Delta \rho_{xx}(H)\rho_{xx}(0)/(\mu_0 H)^2)$ vs. T at various H is plotted. The strong violation of the Kohler's rule given by Eq.(2) is observed.

scale of the excitation which is an order of ~ 4 meV [22]. We believe a close relation exists between the negative MR and the new energy scale suggested in Ref.[22]. In the conventional Fermi liquid metals the MR should obey the Kohler's rule which reads

$$\Delta\rho_{xx}(H) \propto \frac{H^2}{\rho_{xx}(0)}. \quad (2)$$

To examine this relation, we plot $\Delta\rho_{xx}(H)\rho_{xx}(0)/H^2$ against T at various H in the inset of Fig. 4. As shown in Fig. 4(a), this quantity is constant neither in T nor in H , in strong violation of Kohler's rule.

We are now in the position to make a quantitative analysis for the T -linear resistivity, the Hall angle $\cot\theta_H \propto T^2$, and the violation of the Kohler's rule in the MR, all of which signal a fundamental breakdown the Fermi-liquid behavior. All of these peculiar transport properties reminds one of high- T_c cuprates. In the latter materials, two opposing views have been put forth to explain these transport properties. The first is the existence of two distinct relaxation time scales, each associated with the spinon and holon excitation in 2D CuO_2 -planes [3, 4]. However, the existence of such excitations would seem unlikely in the present Kondo system with different electronic structures and different ground states, though we cannot completely exclude this possibility. The second is the modification of the transport quantities arising from the AF spin fluctuation near the QCP. According to the spin fluctuation theory, the transport properties are governed by the staggered susceptibility χ_Q [24, 25]. For instance, ρ_{xx} and R_H are given as,

$$\rho_{xx} \sim \xi_{\text{AF}}^2 T^2 \sim \chi_Q T^2, \quad (3)$$

$$R_H \sim \pm \xi_{\text{AF}}^2 \sim \chi_Q, \quad (4)$$

where ξ_{AF} is the AF correlation length [24]. Since χ_Q obeys the Curie-Weiss law near the QCP, $\chi_Q \propto 1/(T + \Theta)$, ρ_{xx} is proportional to T and R_H is inversely proportional to T , consistent with the present results. Moreover since χ_Q generally exhibits a non-linear H -dependence,

in contrast to χ_0 with a linear H -dependence, the deviation from H -linear dependence of ρ_{xy} shown in Fig. 2(b) is also consistent with Eq.(4). The spin fluctuation theory near the AF QCP predicts that the MR is also strongly influenced by χ_Q and Kohler's rule should accordingly be modified as [25],

$$\frac{\Delta\rho_{xx}(H)}{\rho_{xx}(0)} \propto \left(\frac{\chi_Q H}{\rho_{xx}(0)} \right)^2 \propto (\rho_{xx}(0)\sigma_{xy}(H))^2 \quad (5)$$

where $\sigma_{xy} (\equiv \rho_{xy}/(\rho_{xx}^2 + \rho_{xy}^2))$ is the Hall conductivity. We now examine the MR in accordance with this "modified Kohler's rule", which well explains the MR of high- T_c cuprates [4, 25]. The main panel of Fig. 4 depicts $p (\equiv \Delta\rho_{xx}(H)/\sigma_{xy}^2(H)\rho_{xx}^3(0))$ vs T at several fields. Below $T^* \simeq 20$ K, p is nearly constant in T and H , providing a support for the validity of Eq.(5). (The deviation of p from the high temperature value at 2.5 K is possibly due to the influence of the superconducting fluctuation just above T_c or the pseudogap reported in Ref.[13].) A strong deviation can be seen above T^* . Thus both the Hall effect and the MR at low field below T^* in the coherent region are well described by Eqs.(4) and (5).

Summarizing the salient features in the normal state transport properties of quasi-2D HF superconductor CeCoIn_5 , which is located near the QCP; (1) almost perfect T -linear ρ_{xx} , (2) T^2 -dependent $\cot\theta_H$, (3) the MR which obeys a modified Kohler's rule. All of these peculiar properties are observed in the same temperature range between T_c and $T^* \simeq 20$ K. *These are new hallmarks of the non-Fermi liquid behavior in the transport property* and well explained by the spin fluctuation theory near the QCP. These results also bear striking resemblance to high- T_c cuprates. It should be noted that the ground state of high- T_c cuprates is a Mott insulator while the ground state of CeCoIn_5 appears to be an AF metal. The striking similarity between two different systems implies a universal excitation structure of AF fluctuation near the QCP, which promotes future study.

We thank S. Ohara, Y. Ohkawa, I. Sakamoto, H. Sato, K. Ueda, S. Watanabe, and V. Zlatić for valuable discussions.

-
- [1] T. Moriya, and T. Takimoto, J. Phys. Soc. Jpn, **64**, 960 (1995), P. Coleman *et al.*, J.Phys. C **13** R723 (2001).
 - [2] M. Sigrist and K. Ueda, Rev. Mod. Phys. **63**, 239 (1991).
 - [3] T.R. Chien *et al.*, Phys. Rev. Lett. **67**, 2088 (1991).
 - [4] J.M. Harris *et al.*, Phys. Rev. Lett. **75**, 1391 (1995).
 - [5] C. Petrovic *et al.*, J.Phys. C **13**, L337 (2001).
 - [6] H. Shishido *et al.*, J.Phys. Soc. Jpn **71**, 62(2002).
 - [7] O. Trovarelli *et al.*, Phys. Rev. Lett. **85**, 626 (2000).
 - [8] A. Rosch, Phys. Rev. Lett. **82**, 4280 (1999).
 - [9] G.-q. Zheng *et al.*, Phys. Rev. Lett. **86**, 4664 (2001), Y. Kohori *et al.*, Phys. Rev. B **64**, 134526 (2001).
 - [10] V. S. Zapf *et al.*, Phys. Rev. B **65**, 014506 (2002).
 - [11] A. Fisher *et al.*, Phys. Rev. B **65**, 224509 (2002), P. G. Pagliuso *et al.*, Phys. Rev. B **64**, 100503 (2001).
 - [12] R. Movshovich *et al.* Phys. Rev. Lett. **86**, 5152 (2001).
 - [13] K. Izawa *et al.* Phys. Rev. Lett. **87**, 057002 (2001).
 - [14] V.A. Sidorov *et al.*, Phys. Rev. Lett. **89**, 157004 (2002).
 - [15] A. Fert, and P.M. Levy, Phys. Rev. B **36**, 1907 (1987).
 - [16] P. Coleman, P.W. Anderson, and T.V. Ramakrishnan, Phys. Rev. Lett. **55**, 414 (1985).
 - [17] Y. Onuki *et al.*, J. Phys. Soc. Jpn **58**, 2126 (1989).
 - [18] J. Schoenes and J.J.M. Franse, Phys. Rev. B **33**, 5138 (1986).
 - [19] H. Kontani, and K. Yamada, J. Phys. Soc. Jpn **63**, 2627

- (1994).
- [19] S. Ohhara, private commun.
 - [20] G. Chen *et al.* a preprint.
 - [21] V. Zlatic, J.Phys. F **11**, 2147 (1981), M.C. Aronson *et al.*, Phys. Rev. Lett. **63**, 2311 (1989), F.J. Ohkawa *ibid.* **64**, 2300 (1990)
 - [22] S. Nakatsuji *et al.*, Phys. Rev. Lett. **89**, 106402 (2002).
 - [23] J. Paglione *et al.*, cond-mat/0212502.
 - [24] H. Kontani, K. Kanki, and K. Ueda, Phys. Rev. B **59**, 14723 (1999).
 - [25] H. Kontani, J.Phys. Soc. Jpn, **70**, 1873 (2001).